

Product Information - PLANTIC™ HS Sheet

PLANTIC™ is a high barrier thermoformable, water dissolvable packaging material made predominantly from starch using state of the art technology.

High Barrier packaging material for Thermoforming




Made from high amylose starch, a renewable resource that will lower your packaging greenhouse gas emissions.



Clear, Grease Proof, Water dissolvable, Aroma Capture, Printable, Puncture resistant, extruded film.



Can be formed into trays, pouches, bag liners as primary and secondary packing to replace existing flexible structures.



Ultra-low Gas Barrier Transmission providing extended shelf life, compliments paper as a barrier that maintains recyclability.

APPLICATIONS

PLANTIC™ Mono material is suitable for a variety of applications that require a renewable, dissolvable, barrier sheet. This product is not designed for microwaveable and oven heat applications. PLANTIC™ R+ roll-stock can be used on readily available thermoform packaging machines.

QUALITY

Plantic manufacturing location in Australia is accredited to Food Safety System Certification 22000 (FSSC 22000).

FOOD COMPLIANCE APPROVAL.

This product meets the requirements of Federal Food, Drug and Cosmetics Act. This includes FDA Food Types, as defined in 21CFR176.170(c), III, IVA, V, VIIA, VIII and IX for conditions of use E through G.

PRODUCT CHARACTERISTICS

Thickness Range	250µm to 700µm (+/- 5%) *
Roll Width Range	250-1000mm (+/- 1mm) *

*For any other thickness, width, or Colour requirements, please contact Plantic Technologies Ltd.

TECHNICAL DATA

Barrier Properties

Property	Test Method	Value	Units
Water Vapour Transmission Rate	ASTM F1249-01	<3*	g/m ² /24h @ 38°C and 90%RH
Oxygen Transmission Rate	ASTM F1927-98	<0.5*	cm ³ /m ² /24h @ 23°C, 50%RH

*Test results for 450µm PLANTIC™ R⁺.

* Correlation of measured values should be validated with actual shelf-life analysis.

Physical properties

Test results for 100µm PLANTIC™ Mono

Property	Test Method	Value	Units
Density	ASTM D792	1.33	g/cm ³ (23°C and 50%RH)
Yield (Nominal)	ASTM D4321	1.72	m ² /kg (23°C and 50%RH)
Tensile Modulus	ASTM D882	1709	MPa (23°C and 50%RH)
Tensile Strength	ASTM D882	8.34	MPa (23°C and 50%RH)
Elongation at break	ASTM D882	176	% (23°C and 50%RH)
Impact Strength	ASTM D3420	33	mN/mm (23°C and 50%RH)
OTR		<1	cc/m ² .day.atm (23°C and 50%RH)
Seal Strength		>22	N/15mm

Thermal Properties

Property	Value	Units
Sealing temperature	130-150*	°C
Thermoforming temperatures	90-110**	°C


*Sealing is achieved with compatible PE top lid films. For more seal condition guidelines, please contact Plantic Technologies Ltd.

**For more information on thermoforming conditions (heating and forming time, pressures etc....) [please contact](#)


End of Life Properties

Property	Comment
GHGs	50% less than conventional PET barrier & non barrier
Recyclability Status*	Plantic R+ curb side recyclable

*Subject to evolving country standards currently permitted in North America, Australia, and New Zealand.

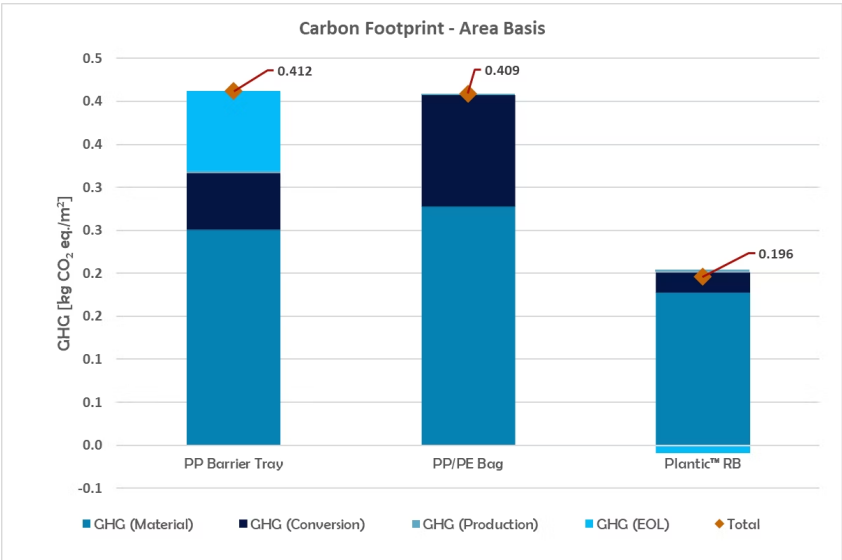

OTR Modelling and Validation

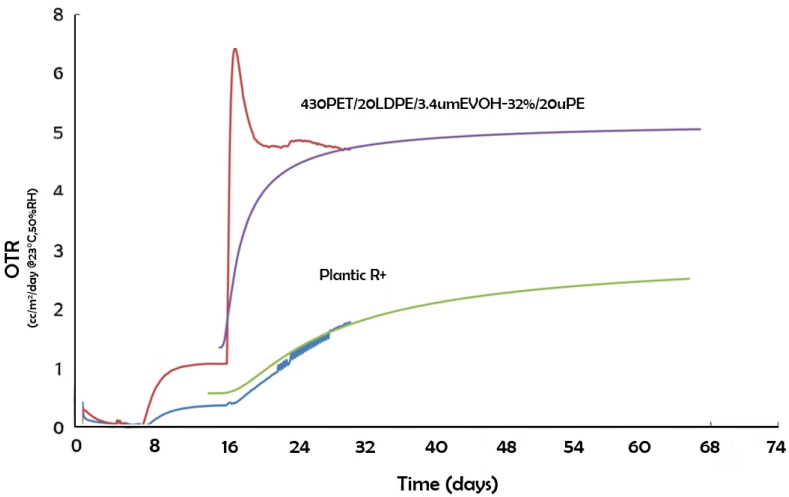

A simulation model is used to predict the time - dependent (transient) oxygen transmission rate (OTR) of the multilayer structures. The model is based on the measured oxygen permeability and diffusivity of the individual skin and barrier layers.

The predicted OTR closely matches the values measured experimentally using a Mocon OTR system. This strong agreement confirms that the observed transient OTR behavior is primarily driven by the high moisture content of the Plantic barrier layer and the diffusion characteristics of the materials Plantic uses.

Draw Ratio Capability

Most rigid thermoformed trays are produced with draw ratios below 3.0, typically in the range of 2.0 to 2.5. This corresponds to standard tray depths of 40–60 mm. Plantic R+ is designed to support deeper draw applications, with draw ratios of up to 3.6. As expected for higher draw ratios, the reduction in material thickness with increasing depth follows the trend shown in the figure below.

